


PBD ISO 8970
ISO 8970

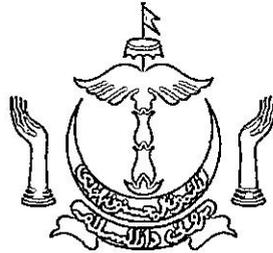

PLAWAI BRUNEI DARUSSALAM
BRUNEI DARUSSALAM STANDARD

Timber Structures – Testing of Joints Made with Mechanical Fasteners – Requirements for Wood Density

MINISTRY OF DEVELOPMENT
NEGARA BRUNEI DARUSSALAM

Copyright Reserved

**Construction Planning and Research Unit
Ministry of Development
Old Airport, Jalan Berakas
Bandar Seri Begawan BB 3510
Negara Brunei Darussalam**

Timber Structures – Testing of Joints Made with Mechanical Fasteners – Requirements for Wood Density

PIAWAI BRUNEI DARUSSALAM

PBD ISO 8970

First Edition

National Foreword

This Brunei Darussalam Standard reproduces verbatim ISO 8970: 1989 and implements it as the Brunei Darussalam National Standard.

This Brunei Darussalam Standard is published under the direction of the Technical Committee on Timber Standards.

Attention is drawn to the fact that this Brunei Darussalam Standard does not confer any immunity from legal obligations in any contract for compliance to the Standard.

The Brunei Darussalam Standards are subject to periodical review according to the current needs of the local industries to keep abreast of progress in the industries concerned. Suggestions of amendments will be recorded and in due course brought to the notice of the committees concerned.

Amendments issued since publication :

Amd No.	Date of issue	Text affected

CONTENTS

Committee Representation		Page (i)
1	Scope	1
2	Normative References.....	1
3	Generals	1
4	Method 1	1
5	Method 2	1

COMMITTEE MEMBERS

The Technical Committee on Timber was entrusted by the Ministry of Development for the preparation of this Brunei Darussalam Standard. The Technical Committee members are as follows:-

- | | | | |
|-----|----------------------------|---|--|
| 1. | Dr. Wong Tuck Meng (Chair) | - | Forestry Department,
Ministry of Industry and Primary Resources. |
| 2. | Rosalind Khan | - | Construction Planning and Research Unit,
Ministry of Development. |
| 3. | Hamiddon Hj Md Said | - | BKS/UBB, DTS, Public Works Department. |
| 4. | Dr. Tan Kha Sheng | - | University Brunei Darussalam. |
| 5. | Dr. Yong Chee Tuan | - | University Brunei Darussalam. |
| 6. | Dr. John Onu Odihi | - | University Brunei Darussalam. |
| 7. | Nicholas Leong Soon Kong | - | Brunei Shell Petroleum. |
| 8. | Raymond Foo Jong Keng | - | Brunei Shell Petroleum. |
| 9. | Rosmin Ramli | - | Brunei Shell Petroleum. |
| 10. | Adnan Hj Bagol | - | Sultan Saiful Rizal Technical College. |
| 11. | Peter Tang | - | Cooper Macdonald Daud Sdn Bhd. |
| 12. | David Price | - | Arkitek Ibrahim. |
| 13. | Arun Nadig | - | Sepakat Setia Perunding |

INTERNATIONAL
STANDARD

ISO
8970

First edition
1989-07-01

**Timber structures — Testing of joints made with
mechanical fasteners — Requirements for wood
density**

*Structures en bois — Essai des assemblages réalisés par organes mécaniques —
Exigences concernant la masse volumique du bois*



Reference number
ISO 8970 : 1989 (E)

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for approval before their acceptance as International Standards by the ISO Council. They are approved in accordance with ISO procedures requiring at least 75 % approval by the member bodies voting.

International Standard ISO 8970 was prepared by Technical Committee ISO/TC 165, *Timber structures*.

© ISO 1989

All rights reserved. No part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from the publisher.

International Organization for Standardization

Case postale 56 • CH-1211 Genève 20 • Switzerland

Printed in Switzerland

Timber structures — Testing of joints made with mechanical fasteners — Requirements for wood density

1 Scope

This International Standard specifies two methods for the selection of wood density for specimens which are to be used in determining by testing the strength and stiffness properties of joints made with mechanical fasteners.

The two methods are equally applicable.

It is assumed that the wood density is normally distributed with a coefficient of variation of about 0,15.

It is emphasized that the density is only one of the properties influencing the strength of a joint. Other relevant properties are, for example, growth ring size and slope of grain.

2 Normative reference

The following standard contains provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the edition indicated was valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent edition of the standard indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 3131 : 1975, *Wood — Determination of density for physical and mechanical tests.*

3 General

This International Standard specifies two methods for the selection of wood density.

The first method is based on all specimens having a density comparable with the characteristic density of the timber to which the test result should be applied; normally the test data can be used directly for calculating characteristic values, etc. of the joints.

NOTE — The characteristic value of a material property corresponds in general to a fractile in the assumed statistical distribution of the particular property. The fractile — normally 0,05 or 0,5 — is specified in the relevant design standard.

The second method is aimed at getting specimens with a uniform density comparable with the mean density of the timber to which the test results should be applied; normally the characteristic values, etc. of the joints are calculated on the basis of corrected test values, F_{cor} , determined from the observed values, F_o , as

$$F_{cor} = F_o \left(\frac{\rho_k}{\rho} \right)^c$$

where

ρ is the density of the wood in which failure took place;

ρ_k is the required characteristic density for the timbers to which the test results should be applied;

c is a power depending on the influence of the wood properties on the properties of the joint. It should be determined by tests or from theoretical considerations.

4 Method 1

4.1 The wood should be of uniform quality and without localized defects that could influence the test results.

4.2 The mean density, ρ_m , of all specimens should satisfy the following condition :

$$\rho_m < 1,15 \rho_k \quad \dots (1)$$

where ρ_k is the required characteristic density for the timbers to which the test results should be applied, in kilograms per cubic metre, determined in accordance with ISO 3131 with mass and volume corresponding to equilibrium at a temperature of $20 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$ and relative humidity of $(65 \pm 5) \%$.

4.3 The density, ρ , of at least 20 % of the specimens should satisfy the following condition :

$$\rho < \rho_k \quad \dots (2)$$

where ρ_k is as in 4.2.

5 Method 2

5.1 The wood should be of uniform quality and without localized defects that could influence the test results.